

This article was downloaded by: [Hai, N. H.]

On: 18 September 2009

Access details: Access Details: [subscription number 915045403]

Publisher Taylor & Francis

Informa Ltd Registered in England and Wales Registered Number: 1072954 Registered office: Mortimer House, 37-41 Mortimer Street, London W1T 3JH, UK



Journal of Experimental Nanoscience

Publication details, including instructions for authors and subscription information:

<http://www.informaworld.com/smpp/title-content=t716100757>

Arsenic removal from water by magnetic $\text{Fe}_{1-x}\text{Co}_x\text{Fe}_2\text{O}_4$ and $\text{Fe}_{1-y}\text{Ni}_y\text{Fe}_2\text{O}_4$ nanoparticles

N. D. Phu ^a; P. C. Phong ^b; N. Chau ^a; N. H. Luong ^a; L. H. Hoang ^b; N. H. Hai ^a

^a Center for Materials Science, Hanoi University of Science, Vietnam National University, Hanoi, Vietnam ^b Faculty of Physics, Hanoi National University of Education, Hanoi, Vietnam

Online Publication Date: 01 September 2009

To cite this Article Phu, N. D., Phong, P. C., Chau, N., Luong, N. H., Hoang, L. H. and Hai, N. H. (2009) 'Arsenic removal from water by magnetic $\text{Fe}_{1-x}\text{Co}_x\text{Fe}_2\text{O}_4$ and $\text{Fe}_{1-y}\text{Ni}_y\text{Fe}_2\text{O}_4$ nanoparticles', *Journal of Experimental Nanoscience*, 4:3, 253 — 258

To link to this Article: DOI: 10.1080/17458080802590474

URL: <http://dx.doi.org/10.1080/17458080802590474>

PLEASE SCROLL DOWN FOR ARTICLE

Full terms and conditions of use: <http://www.informaworld.com/terms-and-conditions-of-access.pdf>

This article may be used for research, teaching and private study purposes. Any substantial or systematic reproduction, re-distribution, re-selling, loan or sub-licensing, systematic supply or distribution in any form to anyone is expressly forbidden.

The publisher does not give any warranty express or implied or make any representation that the contents will be complete or accurate or up to date. The accuracy of any instructions, formulae and drug doses should be independently verified with primary sources. The publisher shall not be liable for any loss, actions, claims, proceedings, demand or costs or damages whatsoever or howsoever caused arising directly or indirectly in connection with or arising out of the use of this material.

Arsenic removal from water by magnetic $\text{Fe}_{1-x}\text{Co}_x\text{Fe}_2\text{O}_4$ and $\text{Fe}_{1-y}\text{Ni}_y\text{Fe}_2\text{O}_4$ nanoparticles

N.D. Phu^a, P.C. Phong^b, N. Chau^a, N.H. Luong^a, L.H. Hoang^b and N.H. Hai^{a*}

^aCenter for Materials Science, Hanoi University of Science, Vietnam National University, Hanoi, Vietnam; ^bFaculty of Physics, Hanoi National University of Education, Hanoi, Vietnam

(Received 24 April 2008; final version received 30 October 2008)

This article studies the effects of Co and Ni replacement in $\text{Fe}_{1-x}\text{Co}_x\text{Fe}_2\text{O}_4$ and $\text{Fe}_{1-y}\text{Ni}_y\text{Fe}_2\text{O}_4$ ($x, y=0, 0.05, 0.1, 0.2, 0.5$) nanoparticles, pH, weight of nanoparticles/mL of water, and time of stirring on the arsenic removal ability. The results showed that a small amount (0.25 g L^{-1}) of Fe_3O_4 nanoparticles after stirring time of 3 min can reduce the arsenic concentration from 0.1 to 0.01 mg L^{-1} . The removal was also affected by the pH of the water. Absorption of arsenic by nanoparticles was effective when pH was smaller than seven and reduced with the increase of pH. At pH of 13, there was a strong release of arsenic ions from arsenic-absorbed nanoparticles back to water. The time of stirring was studied from 1 min to 2 h and the optimal time was about few minutes. Co and Ni's presence was reported to keep saturation magnetisation stable under working conditions. For Co replacement, absorption does not change significantly when $x \leq 0.1$ and slightly reduces when $x > 0.1$. The presence of Ni improved the absorption in most cases.

Keywords: magnetic nanoparticles; ferrites; arsenic removal; water treatment

1. Introduction

Arsenic occurs naturally in rocks, soil, water, air, plants, and animals. It can be further released into the environment through natural activities such as volcanic action, erosion of rocks and forest fires, or through human actions. Higher levels of arsenic tend to be found in ground water sources than in surface water sources of drinking water. Arsenic-contaminated water has been a serious problem especially in Vietnam, Bangladesh and in some other areas in the world (<http://www.epa.gov/safewater/arsenic>) [1]. Human exposure to arsenic can cause both short- and long-term health effects. Short-term or acute effects can occur within hours or days of exposure. Long-term or chronic effects occur over many years. Long-term exposure to arsenic has been linked to cancer of the bladder, lungs, skin, kidneys, nasal passages, liver, and prostate. Short-term exposure to high doses of arsenic can cause other adverse health effects [2,3]. The World Health Organization (WHO) has set a maximum permissible concentration (MPC) value of

*Corresponding author. Email: nhhai@vnu.edu.vn

0.01 mg L⁻¹ which has been applied in many countries. There are many arsenic-removal techniques which have been available such as co-precipitation, adsorption in fixed-bed filters, membrane filtration, anion exchange, electrocoagulation, and reverse osmosis [4,5]. Iron oxides have been reported to have a high affinity for the adsorption of arsenic and arsenate [6–8] due to their ability to form inner-sphere bidentate-binuclear complexes with iron oxides [9,10]. Iron oxide nanoparticles with large surface area are promising for arsenic removal. Some researchers have been paid to study the effects of environment on arsenic adsorption ability of magnetite Fe₃O₄ nanoparticles [8,11]. Magnetite nanoparticles have the highest saturation magnetisation of 90 emu g⁻¹ among iron oxides. Therefore, magnetite nanoparticles can be used to adsorb arsenic ions followed by magnetic decantation. Other iron oxides and hydroxides have been reported to have arsenic ability. However, the magnetic properties of these compounds are much less than that of magnetite. Oxidation of magnetite which resulted in the reduction of the saturation magnetisation was found. Research by our group showed that the replacement of Fe²⁺ in Fe₃O₄ by a small amount of Co²⁺ or Ni²⁺ can improve the oxidation resistance of the compound [13]. Oxidation resistance is an important factor for arsenic removal under atmospheric conditions. In this article, we study arsenic adsorption ability of Fe_{1-x}Co_xFe₂O₄ (Co-ferrites) and Fe_{1-y}Ni_yFe₂O₄ (Ni-ferrites) ($x, y = 0, 0.05, 0.1, 0.2, 0.5$) nanoparticles.

2. Materials and methods

Magnetite particles with size of 15 nm were prepared by conventional co-precipitation of Fe³⁺ and Fe²⁺ ions by OH⁻ at room temperature. In a typical synthesis, 4.17 g of FeCl₃ · 6H₂O and 1.52 g of FeCl₂ · 4H₂O (such that Fe³⁺/Fe²⁺ = 2) were dissolved in 80 mL water (concentration of Fe²⁺ is 0.1 M) with vigorous stirring. A solution of 6 ml NH₄OH 35% was added at the rate of one drop per second at room temperature during constant stirring. Black precipitates of Fe₃O₄ (FeO · Fe₂O₃) were formed and isolated from the solvent by magnetic decantation. Water washing and decantation process were repeated four times to remove excess solution. In a similar way, Fe_{1-x}Ni_xO · Fe₂O₃ and Fe_{1-y}Co_y · Fe₂O₃ with $x = 0.05, 0.1, 0.2, 0.5$ and $y = 0.2, 0.4$ nanoparticles were made by replacing Fe²⁺ by Ni²⁺ and Co²⁺ using NiCl₂ · 6H₂O and CoCl₂ · 6H₂O, respectively. All procedures were conducted under N₂ atmosphere. A Transmission Electron Microscope (TEM) JEM1010-JEOL was used to determine particle size. The structure was examined by X-ray diffractometer (XRD) D5005, Bruker, using Cu-K α radiation. Magnetic properties were measured by Vibrating Sample Magnetometer DMS 880-CTS. Arsenic solution (0.1 mg L⁻¹ of As³⁺) was obtained by dissolving As₂O₃ in doubly distilled water. The adsorption process occurred when 0.25–1.5 g of nanoparticles was stirred in 1 L of arsenic solution for the time of 1–60 min. Then the nanoparticles were collected by an external magnet. The remaining solution was subjected for arsenic concentration by Atomic Absorption Spectroscopy (AAS).

3. Results and discussion

Figure 1 presents the TEM image of the Fe₃O₄ nanoparticles with particle size of 10–16 nm. The particles were almost spherical and had low size dispersity. The mean

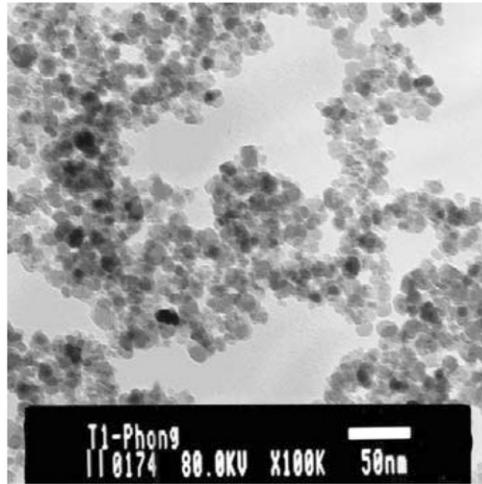


Figure 1. TEM image of the Fe_3O_4 nanoparticles.

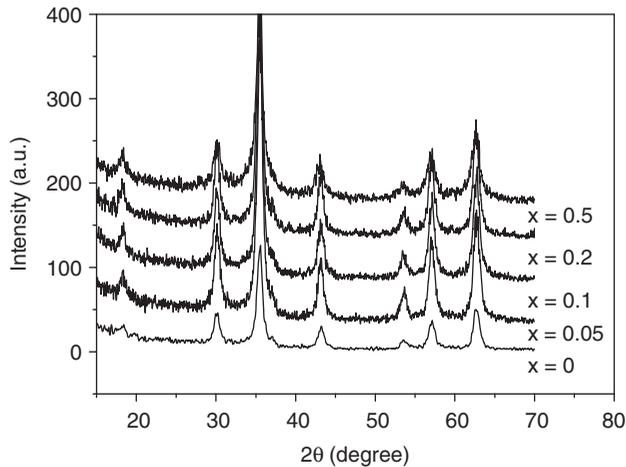


Figure 2. XRD patterns of the magnetite nanoparticles.

particle size was estimated to be 13.3 ± 3.1 nm. The surface area of $77.9 \text{ m}^2 \text{ g}^{-1}$ was calculated for magnetite sample from the mean particle and magnetite density (5.18 g cm^{-3}). XRD patterns of magnetite, Co-ferrites (Figure 2), and Ni-ferrites (not shown) revealed that the particles have the invert spinel crystalline structure as in the bulk phase. The presence of Co^{2+} and Ni^{2+} ions did not change the particle size and reflection peaks significantly. The field dependence of magnetisation showed that all samples were superparamagnetic at room temperature. In an inverse spinel magnetite, half the Fe^{3+} ions were located at A sites and the other half of them, together with the divalent Fe^{2+} ions, were located at B sites. The Co^{2+} and Ni^{2+} ions preferred to replace at B sites.


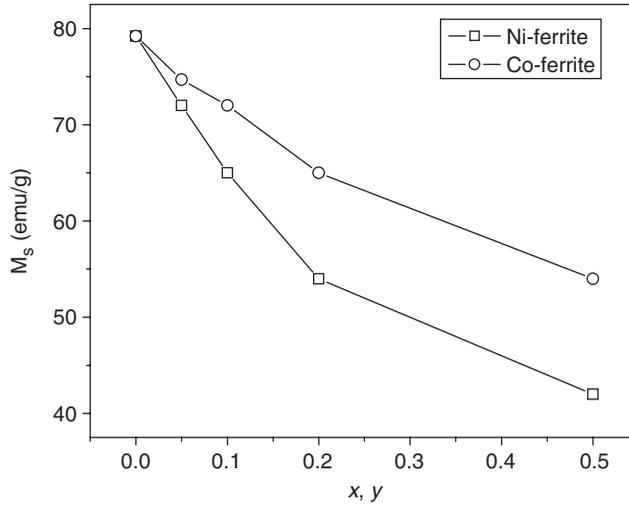


Figure 3. Saturation magnetisation of the Co- and Ni-ferrite as a function of Co^{2+} (x) and Ni^{2+} (y) content.

Therefore, the orientation of spins is as follows:

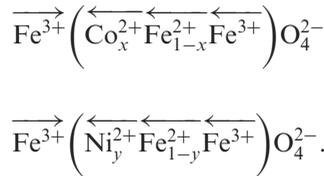

According to Neel’s theory [14], saturation magnetisation for a formula unit of the Co- and Ni-ferrites can be determined by:

$$M_s^{\text{Co-ferrite}} = (4 - 2x)\mu_B$$

$$M_s^{\text{Ni-ferrite}} = (4 - y)\mu_B.$$

The magnetic moment of Ni^{2+} and Co^{2+} ions is $2 \mu_B$ and $3 \mu_B$, respectively. As a result, the saturation magnetisation of the Co- and Ni-ferrites linearly reduces with x and y . Figure 3 presents the saturation magnetisation as a function of Co and Ni content. A linear dependence was found in the samples with Co and Ni content lower than 0.5. At the higher content ($x, y = 0.5$), the Co and Ni atoms can also place at A sites which resulted in the deviation from the linear dependence. Arsenic-adsorption ability of magnetite, Co-, and Ni-ferrites was studied with different conditions of stirring time, concentration of nanoparticles, and pH. Table 1 shows the stirring time dependence of arsenic removal of 1 g L^{-1} of Co-ferrites at neutral pH. The starting concentration of 0.1 mg L^{-1} was reduced about 10 times down to the MPC value of $10 \mu\text{g L}^{-1}$ after stirring for few minutes. The removal process did not seem to depend significantly on the concentration of x in the Co-ferrites. Similar results were found for the Ni-ferrites, in which arsenic concentration was reduced to the MPC value after a few minutes of stirring and the removal did not

Table 1. Arsenic concentration ($\mu\text{g L}^{-1}$) remained in water after removal by 1 g L^{-1} of the Co-ferrites as a function of the stirring time.

Time (min)	$x = 0.05$	$x = 0.1$	$x = 0.2$	$x = 0.5$
1	10	11	6	6.5
3	6	5	8.5	7
7	10	9	4.2	7.8
15	9	12	5	6.9
30	12	4.5	5	11.2
60	4.5	5	8	9.8

change significantly with y . We also studied the effects of the weight of nanoparticles on the removal process. The stirring time was fixed to be 3 min and the weight of samples was changed from 0.25 to 1.5 g L^{-1} with a step of 0.25 g L^{-1} . The results showed that, after 3 min, the optimal weight to reduce arsenic concentration down to the value lower than the MPC was 0.25 g L^{-1} for magnetite and 0.5 g L^{-1} for Co- and Ni-ferrites.

The arsenic adsorption was reported to be independent of pH in the range of 4–10. However, at high pH values, the adsorption reduced significantly. Arsenic was desorbed from the adsorbent at alkaline pH [8]. Our reported results were conducted at pH of 7. After arsenic adsorption, the nanoparticles were stirred under pH of 13 to study the desorption process. Nanoparticles were collected by a magnet and the arsenic concentration in the solution was determined by AAS. Results showed that 90% of the arsenic was desorbed from nanoparticles. The nanoparticles after desorption did not show any difference in arsenic re-adsorption ability. The adsorption–desorption process was repeated four times, which proved that the nanoparticles can be reused for arsenic removal.

4. Conclusion

The presence of Co^{2+} and Ni^{2+} in $\text{Fe}_{1-x}\text{Co}_x\text{Fe}_2\text{O}_4$ and $\text{Fe}_{1-y}\text{Ni}_y\text{Fe}_2\text{O}_4$ with oxidation resistance did not change the arsenic-adsorption ability significantly. With a small amount of materials and simple preparation, we could reduce arsenic concentration to a value lower than the MPC.

Acknowledgment

The authors would like to thank the Asia Research Center, Vietnam National University, Hanoi (DT 34/2007/HD-DT) and the European Commission Project Selectnano-TTC (Contract No. 516922) for finance support.

References

- [1] M. Bissen and F.H. Frimmel, *Arsenic – A review. Part I: Occurrence, toxicity, speciation, mobility*, Acta Hydroch. Hydrob. 31 (2003), pp. 9–18.
- [2] L.C.D. Anderson and K.W. Bruland, *Biogeochemistry of arsenic in natural waters: The importance of methylated species*, Environ. Sci. Technol. 25 (1991), pp. 420–427.

- [3] W.P. Tseng, H.M. Chu, S.W. How, J.M. Fong, C.S. Lin, and S. Yeh, *Prevalence of skin cancer in an endemic area of chronic arsenicism in Taiwan*, J. Nat. Cancer Inst. 40 (1968), pp. 453–463.
- [4] L.G. Twidwell, J. McCloskey, P. Miranda, M. Gale. *Technologies and potential technologies for removing arsenic from process and mine wastewater*, in *Proceedings global symposium on recycling, waste treatment and clean technology*, San Sebastián, Spain, I. Gaballah, J. Hager, R. Solozabal, eds., TMS, Warrendale, PA (1999), pp. 1715–1726.
- [5] M. Bissen and F.H. Frimmel, *Arsenic – A review. Part II: Oxidation of arsenic and its removal in water treatment*, Acta Hydroch. Hydrob. 31 (2003), pp. 97–107.
- [6] M.L. Pierce and C.B. Moore, *Adsorption of arsenite and arsenate on amorphous iron hydroxide*, Water Res. 15 (1982), pp. 1247–1253.
- [7] K.P. Raven, A. Jain, and R.H. Loeppert, *Arsenite and arsenate adsorption on ferrihydrite: Kinetics, equilibrium, and adsorption envelopes*, Environ. Sci. Technol. 32 (1998), pp. 344–349.
- [8] S. Yean, L. Cong, C.T. Yavuz, J.T. Mayo, W.W. Yu, A.T. Kan, V.L. Colvin, and M.B. Tomson, *Effect of magnetite particle size on adsorption and desorption of arsenite and arsenate*, J. Mater. Res. 20 (2005), pp. 3255–3264.
- [9] S. Fendorf, M.J. Eick, and P. Grossl, *Arsenate and chromate retention mechanisms on goethite Surface structure*, Environ. Sci. Technol. 31 (1997), pp. 315–320.
- [10] A. Manceau, *The mechanism of anion adsorption on ironoxides – Evidence for the bonding of arsenate tetrahedra on free Fe(O,OH)(6) edges*, Geochim. Cosmochim. Acta 59 (1995), pp. 3647–3653.
- [11] X.H. Sun and H.E. Doner, *An investigation of arsenate and arsenite bonding structure on goethite by FTIR*, Soil Sci. 161 (1996), pp. 865–872.
- [12] G.A. Waychunas, B.A. Rea, C.C. Fuller, and J.A. Davis, *Surface chemistry of ferrihydrite, Part 1. EXAFS studies of the geometry of coprecipitated and adsorbed arsenate*, Geochim. Cosmochim. Acta 57 (1993), pp. 2251–2269.
- [13] N.H. Hai, N.D. Phu, N. Chau, H.D. Chinh, L.H. Hoang, and D.L. Leslie-Pelecky, *Mechanism for sustainable magnetic nanoparticles under ambient conditions*, J. Korean Phys. Soc. 52 (2008), pp. 1327–1331.
- [14] L. Néel, *Magnetic properties of ferrites: Ferromagnetism and antiferromagnetism*, Ann. de Phys. 3 (1948), pp. 137–198.